

MODERNIZATION SOLUTIONS FOR LOCAL ROADS

V. BOBOC¹ A. BOBOC¹

Abstract: *The paper presents a solution to upgrade the local roads in the Moldavia region, using rigid road structures. For the cement concrete road it had been used local pit gravel partially crushed which replaced a part of the career aggregates. There are analyzed the characteristics of aggregates used in the preparation of cement concrete road and road structures behavior in time under the influence of the climatic factors and road traffic.*

Key words: *cement concrete road, local materials, tensile flexure strength, tensile splitting strength, compression strength, concrete unit weight.*

1. Introduction

Political and economic restructuring in Eastern Europe in the last 25 years has led to substantial changes in the transportation system.

European transport policy objective is to establish a balance between economic development and quality requirements and traffic safety in order to develop a modern transport system.

In European Union, the balance tends towards a transport system centered on road transport.

In Romania, one of the specific objectives in road transport, besides rehabilitation and modernization of national transport infrastructure, is the integration of the local roads in the national infrastructure network [1].

In addition, considering that over 50% of the total length of Romanian roads are the local roads that are not upgraded, a solution that can be used in the Moldavia region is the rigid road structures.

2. Natural pit gravel partially crushed

The natural pit aggregates partially crushed used for the presented local roads are from a pit of Suceava River in Milişăuţi, jud.Suceava. These aggregates are siliceous aggregates that have the following mineralogical composition (determined by X-ray analysis): Quartz - 95%, feldspar plagioclase 3...5% and traces below 1% of serine, limonite, pyrite, lodestone, and kaolinite.

Romanian norm [7] requires in the case of a single layer of concrete cement road the using of minimum two varieties of 8-16 mm and 16-25 mm chippings. In the preparation and realization of cement concrete road with local materials both mandatory chipping varieties were replaced with partially crushed pit gravel 8-16 mm and 16-25 mm.

The characteristics of the aggregates used in the preparation of cement concrete for road are shown in Table 1. Also, Fig. 1 shows the grain size distribution curves of

¹ Department of Roads and Foundations, Civil Engineering and Building Services Faculty, "Gheorghe Asachi" Technical University Iassy

the aggregates used, the granulometric aggregate mixture used to prepare the BcR distribution and the range size of the 4.0 cement concrete for road.

Characteristics of the Milișăuți pit aggregates

Table 1

Nr.	Characteristics	UM	Obtain values					Admissible limits [7]
			Natural sand	Pit aggregates partially crushed				
				0-4	0-4	4-8	8-16	
1.	Sand equivalent	%	98	96	-	-	-	Min.85
2.	Activity coefficient	%	-	1	-	-	-	Max.1.5
3.	Degree of chipping	%	-	-	89	85	91	Min. 65
4.	Shape coefficient	%	-	-	24	16	16	Max. 25
5.	Crushing resistance of aggregates in saturated state	%	-	-	61	76	70	Min. 60
6.	Freeze-thaw resistance / weight loss	%	-	-	1,2	1,0	0,9	Max. 10
7.	Wear with car Los Angeles	%	-	-	21	-	-	Max. 35
					-	19	-	Max. 30
					-	-	15	Max. 25

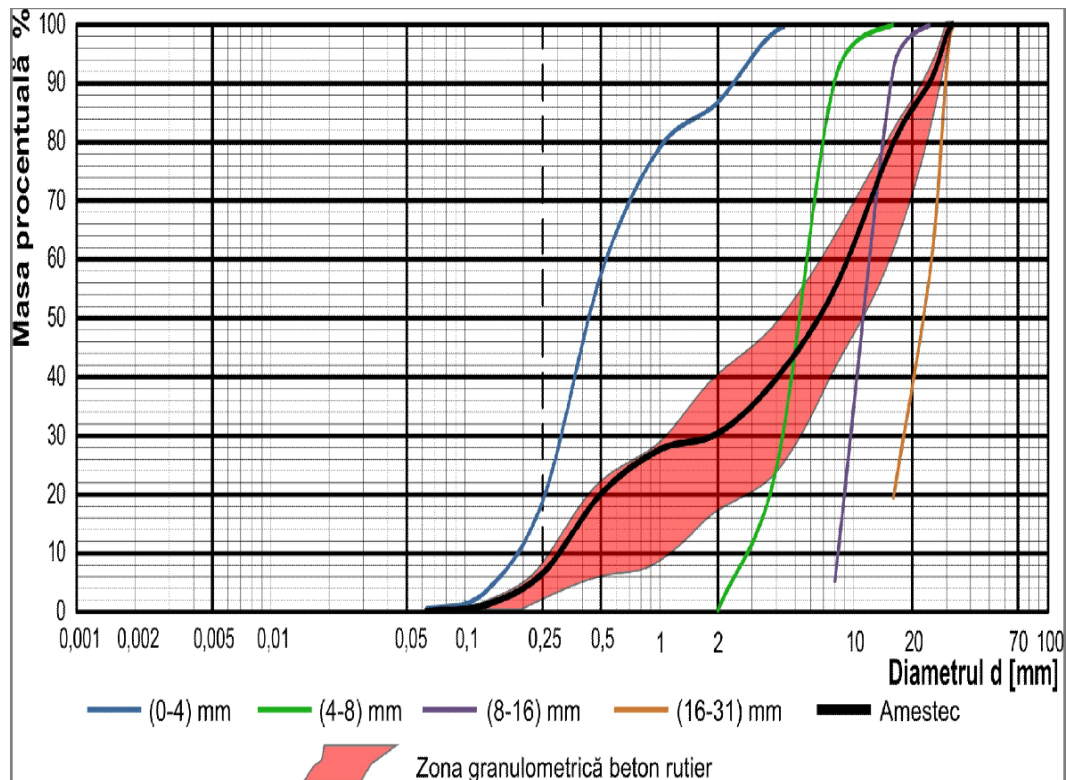


Fig. 1. Grain-size distribution curve for the aggregates and for the aggregates mixture

3. Cement concrete for roads made with pit aggregates

In Romanian norms [7] the Cement Concrete Road notation is BcR 4.0.

The dosage of cement type I 42.5 R was 350 kg/m, the ratio A/C = 0.45, additive dosage of CEMENTOL SPA 94 was 3 ml/kg of cement, resulting a density of the designed concrete of 2358 kg/m³.

The presented road is a municipal two-traffic lane road in town Voitinell located in Suceava County and it was conducted in autumn 2011 with the following composition of the road structure:

- Layer form - the existing pavement with a thickness of 15 cm;

- Foundation layer ballast 0-63 cm - thickness 25cm;
- Stabilized sand + Kraft paper - 2 cm;
- Cement Concrete BcR 4.0 - 20 cm thick.

The physic-mechanical properties of hardened concrete at the age 28 days, RC (compression strength on cubes 150x150x150 mm), Rti (tensile flexure strength on prisms 150x150x600 mm and at the age of 3 years (1,095 days)), RC (compression strength on cores with diameter of 100 mm) and Rtd (tensile splitting strength on cores with a diameter of 100 mm), are shown in table 2.

Physico-mechanical properties of cement concrete BcR 4.0 Table 2

Age	R _C (N/mm ²)		R _{ti} (N/mm ²)	R _{td} (N/mm ²)	Admissible limits [7]
	28 days	1095 days	28 days	1095 days	
Number of samples	72	4	32	4	-
γ _{bet} (kg/m ³)	2358	2376	2358	2319	2390±30
Obtain values	35,38	34,88	4,10	3,26	R _C =35
*S(N/mm ²)	0,96	1,89	0,107	0,175	R _{ti} =4,0
**C _V (%)	2,71	5,42	2,61	5,38	

*S – standard deviation

** C_V – coefficient of variation

Figure 2 shows the variation in time of RC (N/mm²) and the variation of Rt (N/mm²). The ratio RTD / Rti = 0.795 is between the values Walker and Bloem (0.62 ... 0.90) and Efsen and Glarbo (0.67 ... 0.91) as [3].

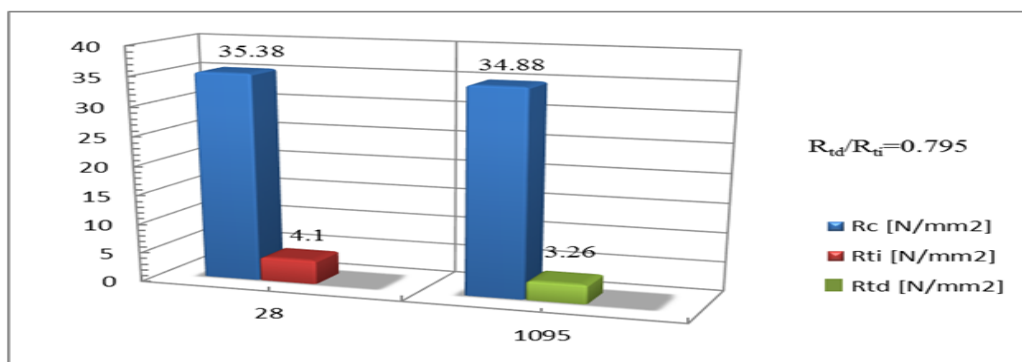


Fig. 2. Variation in time of the mechanical resistance

4. Cement concrete road degradation status

The status of degradation is

characterized by the degradation index: (ID) as in [6] and determined with the relation (1).

$$ID = \frac{\text{number of damaged road panel}}{D_1 + 0,5 \cdot D_2 + 0,5 \cdot D_3 \cdot N / S + 0,3 \cdot D_4} \quad (1)$$

Where:

N- number of road panel per lane;

S - measured surface on a lane (m²);

D₁ - number of settled road panels;

D₂- number of the patching and cracking road panels;

D₃- the surface of the affected area: cracks, corner cracks and longitudinal irregular shape cracks;

D₄ - exfoliated surface.

Degradation index was determined on three homogeneous sectors and the results are shown in Table 3.

The resulting degradation index as presented in [6] is very good, and the only problems on the entire length of the road are:

- Exfoliation of the surface (fig.3)
- Transverse cracks (fig.4).

Degradation Index Table 3

Homogeneous sectors	ID
Km 0+150-0+230 dr.	0,94
Km 1+400-1+490 stg.	0,83
Km 2+000-2+080 dr.	1,04
Mean value	0,94
S	0,085
C _v (%)	9,15



Fig. 3. Exfoliation of the surface



Fig. 4. *Transverse cracks*

4. Conclusions

The use of the rigid cement concrete made of pit partially crushed aggregate for road structures is a viable and economical solution, cheaper by approx. 30% than concrete made with cement road chippings as presented in [7] for upgrading the local roads. The structures made of cement concrete road have an appropriate behavior after 3 years from commissioning.

Road structures with cement concrete made of pit aggregates partially crushed will be monitored annually. It will be analyzed the behavior over time, and if it will be appropriate will be arranged to introduce in the design norms these types of structures.

Other information may be obtained from the addresses: yboboc1956@yahoo.com

References

1. Bota, I.: *Drumuri locale din Romania*, Simpozionul drumuri locale prezent si viitor, Cluj – Napoca, Ed. V.T. Press Cluj – Napoca, 2007.
2. Lucaci, Gh., Costescu, I., Belc, Fl.: *Constructia drumurilor*, Ed.Tehnică, Bucuresti, 2000.
3. Sandor Popovics: *Strength and Related Properties of Concrete: A Quantitative Approach* - John Wiley & Sons, INL – New York 1998.
4. Yoder, J. Witzak, M.M.: *Principles of Pavement Design*, Second Edition John Wiley & Sons, INL – New York 1975.
5. *** C54 - 81: *Instructiuni tehnice pentru incercarea betonului cu ajutorul carotelor*.
6. *** CD 155 - 2000: *Normativ privind*

- determinarea starii tehnice a drumurilor moderne, BTR nr.2/2001.*
7. *** NE 014 - 2002: *Normativ pentru executarea imbracamintilor din beton de ciment rutier .*
8. *** *Normativ pentru dimensionarea ranforsarilor din beton de ciment rutier ale sistemelor rutiere rigide, suple si semirigide, BTR 16/2002*
9. *** NP 116/2002: *Normativ privind*
- alcatuirea structurilor rutiere rigide si suple pentru strazi, BTR 2-3/2005.*
10. *** NP 081 – 2002: *Normativ de dimensionare a structurilor rutiere rigide, BTR 8/2005*
11. *** *Normativ pentru prevenirea si remedierea defectiunilor la imbracaminti rutiere moderne, BTR 8/2013.*